

# Thermal Vibration of Composites and Sandwich Laminates Using Refined Higher Order Zigzag Theory

A. Chakrabarti<sup>1,\*</sup>, S.K. Singh<sup>2</sup>, A.H. Sheikh<sup>3</sup>

<sup>1</sup> Department of Civil Engineering, Indian Institute of Technology, Roorkee-247 667, India

<sup>2</sup> Department of Civil Engineering, School of Engineering, Shiv Nadar University, Dadri, U. P. India

<sup>3</sup> School of Civil, Environment and Mining Engineering, University of Adelaide, North Terrace, Adelaide, SA 5005, Australia

Received 22 January 2013; accepted 14 March 2013

## ABSTRACT

Vibration of laminated composite and sandwich plate under thermal loading is studied in this paper. A refined higher order theory has been used for the purpose. In order to avoid stress oscillations observed in the implementation of a displacement based finite element, the stress field derived from temperature (initial strains) have been made consistent with total strain field. So far no study has been reported in literature on the thermal vibration problem based on the refined higher order theory using a FE model. Numerical results are presented for thermal vibration problems to study the influence of boundary conditions, ply orientation and plate geometry on the natural frequencies of these structures.

© 2013 IAU, Arak Branch. All rights reserved.

**Keywords:** Finite element; Higher order; Laminated composites; Thermal load

## 1 INTRODUCTION

**D**UE to increasing use of fibrous composite materials in various structural members subjected to high temperatures, it is desirable to accurately predict the vibration response of thermally stressed laminated composite and sandwich plates. This study is motivated by the lack of finite element results for natural frequencies of laminated composite and sandwich plates under thermal loading. Only few publications exist for the vibration of laminated composite and sandwich plates under thermal loading. Noor and Burton [1] presented a three dimensional analytical solution for the vibration of thermally stressed laminated angle-ply composite plates. Matsunaga [2] studied free vibration and stability of angle-ply composite and sandwich plates using two dimensional global higher order shear deformation theory subjected to thermal loading. Several two dimensional refined higher order shear deformation theories have been proposed to analyze the response of laminated composite plates. Global higher order plate theories (HSDT) were proposed by Reddy and Phan [3], Putcha and Reddy [4], Tessler et al. [5], Ganapathi and Makhecha [6]), Shi et al. [7] and Khare et al. [8]. Various layer wise and individual theories have been presented to obtain accurate solution at ply level by Carrera [9], Nosier et al. [10] and Cho et al. [11]. Although such types of theories have been proved to be one of the best alternatives to three dimensional elasticity solutions, these theories are computationally expensive to obtain the accurate solutions. Since the total number of unknowns increases dramatically as the number of layers increases. A number of third order theories [12-16] in which the in-plane displacement are assumed to be a cubic expression of the thickness coordinate and out of plane displacement to be a quadratic expression. Kapuria and Achary [16] presented a new zigzag theory based on zigzag third-order variation of in-plane displacements for laminated plates subjected to thermal loading. Matsunaga [17] evaluated interlaminar stresses and displacements in cross-ply multilayered composite and sandwich plates subjected to

\* Corresponding author. Tel.: +91 1332 285844 ; Fax: +91 1332 275568.  
E-mail address: anupam1965@yahoo.co.uk (A. Chakrabarti).

thermal loadings using two-dimensional global higher-order deformation theory. Wang et al. [18] studied the response of dynamic interlaminar stresses in laminated composite plates with piezoelectric layers using an analytical approach based on the layer wise theories.


Zhen and Wanji [19] presented global-local higher order shear deformation theory which satisfies the free surface conditions and the geometric and stress continuity conditions at interfaces for angle ply laminated plates. Thermal buckling behavior of cross and angle-ply laminated composite and sandwich plates subjected to thermal loading have been analyzed by Matsuanga [20, 21]. Vibration and stability problem of angle-ply laminated composite and sandwich plates subjected to thermal loading using global higher order shear deformation theory is presented by Matsuanga [22]. However, finite element based solutions are also needed to validate the analytical solutions. On the other hand many publications were reported in the literatures on thermal buckling of conventional isotropic material, composite and sandwich laminates. However, there is lack of study on vibration under thermal loading based on the refined plate theory especially using a finite element approach.

The present study is focused to fill the above void in the literature. In the present paper natural frequencies of laminated composite and sandwich plates subjected to thermal loading have been studied for the first time by using FE method based on a refined higher order zigzag theory.

## 2 FORMULATION

The in-plane displacement fields Fig. 1 are taken as below:

$$u_\alpha = u_\alpha^0 + \sum_{k=0}^{n_u-1} S_\alpha^k (z - z_k^u) H(z - z_k^u) + \sum_{k=0}^{n_l-1} T_\alpha^k (z - z_k^l) H(z - z_k^l) + \xi_\alpha z^2 + \varphi_\alpha z^3 \quad (1)$$

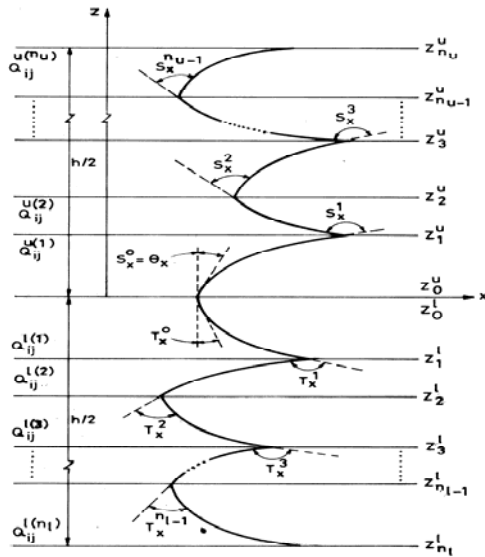

**Fig. 1**  
Lamination layout and in-plane displacement across the cross-section of a plate.

where  $u_\alpha^0$  denotes the in-plane displacement of any point on mid surface,  $n_u$  and  $n_l$  represent number of upper and lower layers respectively.  $S_\alpha^k, T_\alpha^k$  are the slopes of  $k$ -th layer corresponding to upper and lower layers respectively,  $\xi_\alpha, \varphi_\alpha$  are the higher order unknown terms,  $H(z - z_k^u), H(z - z_k^l)$  are unit step functions and the subscript  $\alpha$  represents the co-ordinate directions [ $\alpha = 1, 2$  i.e.,  $x, y$  in this case] respectively and

$$u_3 = w(x, y) \quad (2)$$

The stress-strain relationship of a lamina, say  $k^{\text{th}}$  lamina having any fiber orientation with respect to structural axes system ( $x$ - $y$ - $z$ ) may be expressed as:

$$\bar{\sigma} = [\bar{Q}]_k \{\bar{\varepsilon}\} \quad (3)$$

The rigidity matrix  $[\bar{Q}]_k$  can be evaluated by material properties and fibre orientation following usual techniques for laminated composites.

Now by utilizing the transverse shear stress free boundary condition at the top and bottom of the plate,  $\sigma_{3\alpha|z=\pm h/2} = 0$ , the components  $\xi_\alpha$  and  $\varphi_\alpha$  could be expressed as:

$$\varphi_\alpha = -\frac{4}{3h^2} \left\{ w_{,\alpha} + \frac{1}{2} \left( \sum_{k=0}^{n_u-1} S_\alpha^k + \sum_{k=0}^{n_l-1} T_\alpha^k \right) \right\} \quad (4)$$

and

$$\xi_\alpha = -\frac{1}{2} \left( \sum_{k=0}^{n_u-1} S_\alpha^k - \sum_{k=0}^{n_l-1} T_\alpha^k \right) \quad (5)$$

Similarly by imposing the transverse shear stress continuity conditions at the layer interfaces the following expressions for  $S_\alpha^k$  and  $T_\alpha^k$  are obtained as below:

$$S_\alpha^k = a_{\alpha\gamma}^k (w_{,\gamma} + \psi_\gamma) + b_{\alpha\gamma}^k w_{,\gamma} \quad (6)$$

and

$$T_\alpha^k = c_{\alpha\gamma}^k (w_{,\gamma} + \psi_\gamma) + d_{\alpha\gamma}^k w_{,\gamma} \quad (7)$$

where  $a_{\alpha\gamma}^k, b_{\alpha\gamma}^k, c_{\alpha\gamma}^k, d_{\alpha\gamma}^k$  are constants depending on material and geometric properties of individual layers,  $w_{,\gamma}$  is the derivatives of transverse displacement while  $\gamma = 1, 2$  and  $S_\alpha^0 = \psi_\alpha$  is the rotation of normal at the mid surface about co-ordinate directions.

By using Eqs. (2)-(6) the strain vector can be evaluated as:

$$\{\bar{\varepsilon}\} = [H] \{\varepsilon\} \quad (8)$$

where  $\{\bar{\varepsilon}\}$  is the strain field vector ( $5 \times 1$ ) and  $\{\varepsilon\}$  is the strain vector ( $17 \times 1$ ) at the reference plane (i.e., at the mid plane),  $[H]$  is the matrix ( $5 \times 17$ ) consists of terms containing  $z$  and in order to avoid the difficulties associated with  $C^1$  continuity, the derivatives of  $w$  with respect to  $x$  and  $y$  are expressed in terms of two new variables as follows:

$$w_{,1} = \frac{\partial w}{\partial x} = w_1 \quad \text{and} \quad w_{,2} = \frac{\partial w}{\partial y} = w_2 \quad (9)$$

which helps to define all the variables as  $C^0$  continuous.

$$\{\varepsilon\}^T = \left\{ \frac{\partial u_1^0}{\partial x}, \frac{\partial u_2^0}{\partial y}, \frac{\partial u_2^0}{\partial x} + \frac{\partial u_1^0}{\partial y}, \frac{\partial w_1}{\partial x}, \frac{\partial w_2}{\partial y}, \frac{\partial w_2}{\partial x}, \frac{\partial w_1}{\partial y}, \frac{\partial \psi_1}{\partial x}, \frac{\partial \psi_2}{\partial y}, \frac{\partial \psi_2}{\partial x}, \frac{\partial \psi_1}{\partial y}, \psi_1, \psi_2, \frac{\partial w}{\partial x}, \frac{\partial w}{\partial y}, w_1, w_2 \right\} \quad (10)$$

The strain displacement relation may be written as below,

$$\{\varepsilon\} = [B]\{\delta\} \quad (11)$$

where  $[B]$  is the strain-displacement matrix and  $\{\delta\}$  is the element nodal unknown vector.

Thermal strain due to temperature change is given by:

$$\{\varepsilon_{th}\} = \{\alpha_x \Delta T, \alpha_y \Delta T, \alpha_{xy} \Delta T, 0, 0\}^T \quad (12)$$

In which  $\Delta T$  is the change of temperature/moisture concentration with respect to reference temperature/moisture concentration,  $\alpha_x, \alpha_y, \alpha_{xy}$  are the thermal expansion coefficients in the structural axis ( $x$ - $y$ ) system. Therefore, the net strain may be written as:

$$\{\bar{\varepsilon}_n\} = \{\bar{\varepsilon}\} - \{\varepsilon_{th}\} \quad (13)$$

For the present study, a nine noded  $C^0$  continuous isoparametric element with seven nodal unknowns (i.e.,  $u_1, u_2, w, \psi_1, \psi_2, w_1, w_2$ ) are used to develop the proposed finite element model. The generalized displacements included in the present theory can be expressed as follows,

$$u_1 = \sum_{i=1}^9 N_i u_i, u_2 = \sum_{i=1}^9 N_i v_i, w = \sum_{i=1}^9 N_i w_i, \psi_1 = \sum_{i=1}^9 N_i \psi_{1i}, \psi_2 = \sum_{i=1}^9 N_i \psi_{2i}, w_1 = \sum_{i=1}^9 N_i w_{1i}, w_2 = \sum_{i=1}^9 N_i w_{2i} \quad (14)$$

where  $N_i$  are the shape functions for the nine noded isoparametric finite element.

By applying virtual work method one can get,

$$[k]\{\delta\} = \{P\} \quad (15)$$

where  $[k]$  is the element stiffness matrix and  $\{P\}$  is the element nodal load vector as written below,

$$[k] = \iint [B]^T [D] [B] dx dy \quad (16a)$$

where  $[B]$  is the strain displacement matrix,

$$[D] = \sum_{k=1}^n \int [H]^T [\bar{Q}_k] [H] dz \quad (16b)$$

Is the rigidity matrix and  $n$  is the number of layers, respectively.

$$\{P\} = \iint [N]^T q dx dy \quad (17)$$

where  $[N]$  is the shape functions matrix and  $q$  is the intensity of transverse load, respectively.

Thermal loading may also be obtained as below,

$$[F] = \iint [B]^T [H]^T [F^N] dx dy \quad (18)$$

where

$$\{F^N\}^T = [N_x^N \ N_y^N \ N_{xy}^N \ 0 \ 0 \ 0 \ \dots\dots] \quad (19a)$$

and

$$\{N_x^N \ N_y^N \ N_{xy}^N\}^T = \sum_{k=1}^n \int_{z_{k-1}}^{z_k} \{\bar{Q}_{ij}\}_k \{\varepsilon_{th}\} dz \quad (19b)$$

where  $i, j = 1, 2, 6$  and  $\{\varepsilon_{th}\}$  is the thermal strain components.

It can be observed that the total strain field is always interpolated to a lower order when compared to the thermal strain fields. Hence, thermal strain fields have been consistently reconstituted to the order of in-plane normal strain field to get accurate strains and stresses over the element domain [23]. The following thermal cases are considered:

#### Case 1

Temperature uniform across the depth

$$\begin{Bmatrix} \varepsilon_x \\ \varepsilon_y \\ \varepsilon_{xy} \end{Bmatrix} = \begin{Bmatrix} \alpha_x \\ \alpha_y \\ \alpha_{xy} \end{Bmatrix} \Delta T \quad (20)$$

where

$$\begin{Bmatrix} \alpha_x \\ \alpha_y \\ \alpha_{xy} \end{Bmatrix} = \begin{bmatrix} c^2 & s^2 & -2cs \\ s^2 & c^2 & 2cs \\ cs & -cs & c^2 - s^2 \end{bmatrix} [Q]_k \begin{Bmatrix} \alpha_1 \\ \alpha_2 \\ \alpha_{12} \end{Bmatrix}_k \quad (21)$$

where  $\alpha_1, \alpha_2, \alpha_{12}$  are thermal expansion coefficient in the material axis system and  $c = \cos\theta$ ,  $s = \sin\theta$  and  $\theta$  is the angle between principal material axis and structural axis system.

In this case,  $\Delta T = T$ , therefore, thermal force

$$\{F\} = \iiint [B]^T [H]^T \begin{Bmatrix} \alpha_x \\ \alpha_y \\ \alpha_{xy} \end{Bmatrix} T dv \quad (22)$$

#### Case 2

Temperature varying across the depth, thermal force,

$$\{F\} = \iiint [B]^T [H]^T \begin{Bmatrix} \alpha_x \\ \alpha_y \\ \alpha_{xy} \end{Bmatrix} \cdot \left[ \frac{1}{2}(T_U + T_L) + \frac{z}{h}(T_U - T_L) \right] dv \quad (23)$$

where,  $T_U$  = Temperature at the top surface and  $T_L$  = Temperature at the bottom surface.

The element mass matrix can be written as:

$$[m^e] = \sum_{k=1}^{n_u + n_l} \int \rho_k [C]^T [F]^T [F] [C] dx dy dz \quad (24)$$

where  $\rho_k$  is the mass density of the kth layer and  $[C]$  is the shape function matrix.

Also the element geometric strain vector may be expressed as:

$$\{\varepsilon_G\} = \begin{bmatrix} \frac{1}{2} \left( \frac{\partial \bar{w}}{\partial x} \right)^2 + \frac{1}{2} \left( \frac{\partial \bar{u}}{\partial x} \right)^2 + \frac{1}{2} \left( \frac{\partial \bar{v}}{\partial x} \right)^2 \\ \frac{1}{2} \left( \frac{\partial \bar{w}}{\partial y} \right)^2 + \frac{1}{2} \left( \frac{\partial \bar{w}}{\partial y} \right)^2 + \frac{1}{2} \left( \frac{\partial \bar{w}}{\partial y} \right)^2 \\ \left( \frac{\partial \bar{w}}{\partial x} \right) \left( \frac{\partial \bar{w}}{\partial y} \right) + \left( \frac{\partial \bar{u}}{\partial x} \right) \left( \frac{\partial \bar{u}}{\partial y} \right) + \left( \frac{\partial \bar{v}}{\partial x} \right) \left( \frac{\partial \bar{v}}{\partial y} \right) \end{bmatrix} = \frac{1}{2} \begin{bmatrix} \frac{\partial \bar{w}}{\partial x} & 0 & \frac{\partial \bar{u}}{\partial x} & 0 & \frac{\partial \bar{v}}{\partial x} & 0 \\ 0 & \frac{\partial \bar{w}}{\partial y} & 0 & \frac{\partial \bar{u}}{\partial y} & 0 & \frac{\partial \bar{v}}{\partial y} \\ \frac{\partial \bar{w}}{\partial y} & \frac{\partial \bar{w}}{\partial x} & \frac{\partial \bar{u}}{\partial y} & \frac{\partial \bar{u}}{\partial x} & \frac{\partial \bar{v}}{\partial y} & \frac{\partial \bar{v}}{\partial x} \end{bmatrix} \begin{Bmatrix} \frac{\partial \bar{w}}{\partial x} \\ \frac{\partial \bar{w}}{\partial y} \\ \frac{\partial \bar{u}}{\partial x} \\ \frac{\partial \bar{u}}{\partial y} \\ \frac{\partial \bar{v}}{\partial x} \\ \frac{\partial \bar{v}}{\partial y} \end{Bmatrix} \quad (25)$$

$$= \frac{1}{2} [A_G] [\theta] = \frac{1}{2} [A_G] [G] [\Delta] \quad (26)$$

With the matrix  $[G]$  in the above equation, the geometric stiffness matrix  $[k_g]$  of an element can be derived and may be written as:

$$[k_g] = \sum_{i=1}^{n_u+n_v} \iiint [G]^T [S^k] [G] dx dy dz \quad (27)$$

where  $[S^k]$  is the in-plane stress components of the  $k$ -th layer .

For the linear thermal buckling problems, the stability equation can be expressed as:

$$([K] - \lambda [K_G]) \{\delta\} = 0 \quad (28)$$

In which  $[K]$  and  $[K_G]$  are the global elastic and geometric stiffness matrix and  $\lambda$  is the critical temperature parameter, respectively.

In the first step, a static problem is solved to calculate thermal stresses at the gauss points of different elements for assumed temperature rise. These thermal stresses are then used to form the matrix  $[S^k]$  of the geometric stiffness matrix and the linear thermal buckling problem is solved to calculate the critical buckling temperature. Finally, thermal vibration problem is solved as a Eigen value problem by taking different temperatures just below the calculated critical buckling temperature.

The equation of thermal vibration may be written as:

$$([K'] - \omega^2 [M]) \{\delta\} = 0 \quad (29)$$

where  $[K'] = [K] - \lambda [K_G]$  and,  $[K']$  is the reduced stiffness matrix,  $[M]$  is the mass matrix,  $\lambda$  is a fraction of critical buckling temperature and  $\omega$  is the frequency of thermal vibration, respectively.

A computer program has been written as per the above formulation. The boundary conditions used in different cases are as follows:

1. Simply supported boundary conditions on all sides (SSSS)

$$u_1 = u_2 = w = \Psi_1 = w_1 = 0 \text{ at } x = 0, a$$

$$u_1 = u_2 = w = \Psi_2 = w_2 = 0 \text{ at } y = 0, b$$

2. Clamped boundary conditions on all sides (CCCC)

$$u_1 = u_2 = w = \Psi_1 = \Psi_2 = w_1 = w_2 = 0 \text{ at } x = 0, a \text{ and } y = 0, b$$

### 3 NUMERICAL RESULTS AND DISCUSSIONS

In this section, various numerical examples have been solved on the vibration of laminated composite and sandwich plates under thermal loading. A number of numerical problems with uniform temperature in the plane of the plate have been solved considering different boundary conditions, ply orientations, thickness ratio and aspect ratio. The results obtained by using the proposed finite element method is first validated with the published results and many new results are generated for future reference as there is very few results available in the literature on the present problem based on the refined theories.

#### 3.1 Ten layer simply supported angle-ply laminated composite square plates

*Example 1:* In this example, 10 layer angle-ply ( $\theta = 45^\circ$ ) laminated composite plate subjected to uniform temperature rise throughout the thickness has been investigated. The corresponding material properties (dimensionless) for the angle-ply composite plate are as follows:

$$E_1 / E_2 = 15, \quad G_{12} = G_{13} = 0.5E_2, \quad G_{23} = 0.3356E_2, \quad \nu_{12} = 0.3, \quad \nu_{23} = 0.49, \quad \alpha_1 / \alpha_0 = 0.015, \quad \alpha_2 / \alpha_0 = 1.0, \quad \rho = 1$$

The normalized critical temperature is defined as follows:

$\lambda_{cr} = \alpha_0 T$  where  $T$  is the critical temperature,  $\alpha_0$  is the normalization factor which is taken as  $= 10^{-6}$ , the normalized natural frequency has been defined as  $\Omega = \omega h \sqrt{\rho / E_2}$ . Normalized natural frequencies and critical temperatures (first mode) obtained for different thickness ratio ( $a/h$ ) are shown in Table 1., where  $a$  is the planar dimension of the plate in  $x$ -direction and  $h$  is the total thickness of the plate. The present results (Mesh: 12 x12) are very close to Matsuanaga [22].

**Table 1**

Normalized natural frequency and critical temperature of 10 layer angle-ply [ $\theta / - \theta / \dots / - \theta$ ]<sub>10</sub> square plate with different thickness ratio ( $\theta = 45^\circ$ )

| $a/h$ | $\Omega$                |                         | $\lambda_{cr}$          |                         |
|-------|-------------------------|-------------------------|-------------------------|-------------------------|
|       | Present                 | Matsunaga [22]          | Present                 | Matsunaga [22]          |
| 100   | $0.1605 \times 10^{-2}$ | $0.1595 \times 10^{-2}$ | $0.1697 \times 10^{-2}$ | $0.1675 \times 10^{-2}$ |
| 50    | $0.6368 \times 10^{-2}$ | $0.6342 \times 10^{-2}$ | $0.6675 \times 10^{-2}$ | $0.6620 \times 10^{-2}$ |
| 20    | $0.3805 \times 10^{-1}$ | $0.3811 \times 10^{-1}$ | $0.3810 \times 10^{-1}$ | $0.3826 \times 10^{-1}$ |
| 10    | 0.1339                  | 0.1355                  | 0.1172                  | 0.1209                  |
| 5     | 0.3961                  | 0.4017                  | 0.2531                  | 0.2656                  |

*Example 2:* This problem has been solved for 10 layer angle-ply ( $\theta = 15^\circ$ ) laminated composite plate subjected to uniform temperature rise throughout the thickness has been investigated. The material properties are same as in Example 1. Normalized natural frequencies and critical temperatures obtained for different thickness ratio ( $a/h$ ) are shown in Table 2. The present results (Mesh: 12x12) are in good agreement with Matsuanaga [22].

**Table 2**

Normalized natural frequency and critical temperature of 10 layer angle-ply [ $\theta / - \theta / \dots / - \theta$ ]<sub>10</sub> square plate with different thickness ratio ( $\theta = 15^\circ$ )

| $a/h$ | $\Omega$                |                         | $\lambda_{cr}$          |                         |
|-------|-------------------------|-------------------------|-------------------------|-------------------------|
|       | Present                 | Matsunaga [22]          | Present                 | Matsunaga [22]          |
| 100   | $0.1336 \times 10^{-2}$ | $0.1328 \times 10^{-2}$ | $0.1123 \times 10^{-2}$ | $0.1161 \times 10^{-2}$ |
| 50    | $0.5306 \times 10^{-2}$ | $0.5286 \times 10^{-2}$ | $0.4419 \times 10^{-2}$ | $0.4600 \times 10^{-2}$ |
| 20    | $0.3208 \times 10^{-1}$ | $0.3302 \times 10^{-1}$ | $0.2633 \times 10^{-1}$ | $0.2700 \times 10^{-1}$ |
| 10    | 0.1163                  | 0.1163                  | $0.8894 \times 10^{-1}$ | $0.8899 \times 10^{-1}$ |
| 5     | 0.3588                  | 0.3592                  | 0.2045                  | 0.2124                  |

### 3.2 Simply supported square sandwich $[\theta/-\theta/.../-\theta]_{10}$ [Core] $[-\theta/\theta/.../\theta]_{10}$ plate

In this example, a 21 layer angle-ply ( $\theta = 45^\circ$ ) sandwich plate has been analyzed with the same temperature loadings mentioned above. The material properties (dimensionless) of individual layers are as given below: Face sheets (total thickness  $h_f$ )

$$E_1 / E_2 = 19, \quad G_{12} = G_{13} = 0.52E_2, \quad G_{23} = 0.338E_2, \quad \nu_{12} = 0.32, \quad \nu_{23} = 0.49, \quad \alpha_1 / \alpha_0 = 0.001, \quad \alpha_2 / \alpha_0 = 1.0, \quad \rho =$$

Core (thickness  $h_c$ )

$$E_1 = 3.2 \times 10^{-5}, \quad E_2 = 2.9 \times 10^{-5}, \quad E_3 = 0.4, \quad G_{12} = 2.4 \times 10^{-3}, \quad G_{13} = 0.7.9 \times 10^{-2}, \quad G_{23} = 6.6 \times 10^{-2}, \\ \nu_{12} = 0.99, \quad \nu_{23} = \nu_{32} = 3.0 \times 10^{-5}, \quad \alpha_1 = \alpha_2 = 1.36\alpha_0, \quad \rho_c = 0.07\rho$$

The Normalized natural frequencies and critical temperatures obtained for different thickness ratio by varying the face thickness ( $h_f$ ) to total thickness ( $h$ ) ratio are shown in Table 3. It may be observed in Table 3. that the present results are again closer to the results given by Matsunaga [22].

**Table 3**

Normalized natural frequency and critical temperature of angle-ply  $[\theta/-\theta/.../-\theta]_{10}$  [Core] $[-\theta/\theta/.../\theta]_{10}$  sandwich square plate ( $\theta = 45^\circ$ ) with simply supported boundary conditions with different thickness ratio ( $a/h$ )

| $h_f/h$ | $a/h$ | $\Omega$                |                         | $\lambda_{cr}$          |                         |
|---------|-------|-------------------------|-------------------------|-------------------------|-------------------------|
|         |       | Present                 | Matsunaga [22]          | Present                 | Matsunaga [22]          |
| 0.3     | 100   | $0.2463 \times 10^{-2}$ | $0.2426 \times 10^{-2}$ | $0.5297 \times 10^{-2}$ | $0.5130 \times 10^{-2}$ |
|         | 50    | $0.9631 \times 10^{-2}$ | $0.9509 \times 10^{-2}$ | $0.2024 \times 10^{-1}$ | $0.1973 \times 10^{-1}$ |
|         | 20    | $0.5291 \times 10^{-1}$ | $0.5261 \times 10^{-1}$ | $0.9773 \times 10^{-1}$ | $0.9664 \times 10^{-1}$ |
|         | 10    | 0.1580                  | 0.1587                  | 0.2178                  | 0.2198                  |
|         | 5     | 0.3858                  | 0.3895                  | 0.3295                  | 0.3306                  |
| 0.2     | 100   | $0.2482 \times 10^{-2}$ | $0.2462 \times 10^{-2}$ | $0.5808 \times 10^{-2}$ | $0.5805 \times 10^{-2}$ |
|         | 50    | $0.9758 \times 10^{-2}$ | $0.9692 \times 10^{-2}$ | $0.2282 \times 10^{-1}$ | $0.2252 \times 10^{-1}$ |
|         | 20    | $0.5505 \times 10^{-1}$ | $0.5487 \times 10^{-1}$ | 0.1161                  | 0.1154                  |
|         | 10    | 0.1714                  | 0.1718                  | 0.2813                  | 0.2826                  |
|         | 5     | 0.4303                  | 0.4325                  | 0.4425                  | 0.4471                  |
| 0.1     | 100   | $0.2326 \times 10^{-2}$ | $0.2322 \times 10^{-2}$ | $0.6576 \times 10^{-2}$ | $0.6358 \times 10^{-2}$ |
|         | 50    | $0.9204 \times 10^{-2}$ | $0.9201 \times 10^{-2}$ | $0.2571 \times 10^{-1}$ | $0.2570 \times 10^{-1}$ |
|         | 20    | $0.5408 \times 10^{-1}$ | $0.5410 \times 10^{-1}$ | 0.1418                  | 0.1419                  |
|         | 10    | 0.1825                  | 0.1826                  | 0.4026                  | 0.4033                  |
|         | 5     | 0.5005                  | 0.5003                  | 0.7551                  | 0.7542                  |

### 3.3 Simply supported 1 layer orthotropic ( $0^\circ$ ) and 3 layer orthotropic ( $0^\circ/90^\circ/0^\circ$ ) plates

In this section, simply supported 1 layer ( $0^\circ$ ) and 3 layer orthotropic plate ( $0^\circ/90^\circ/0^\circ$ ) subjected to uniform temperature loading conditions has been analyzed. The Normalized natural frequencies and critical temperatures obtained for different thickness ratio are presented in Table 4. All these are new results.

### 3.4 Simply supported square sandwich ( $[0^\circ/90^\circ/0^\circ/.../0^\circ]_{10}$ [Core] $[90^\circ/0^\circ/90^\circ/.../0^\circ]_{10}$ ) plate

In this example, a 21 layer sandwich plate has been analyzed with the same temperature loadings mentioned above. The material properties (dimensionless) of individual layers are as given below:

Face sheets (total thickness  $h_f$ )

$$E_1 / E_2 = 19, \quad G_{12} = G_{13} = 0.52E_2, \quad G_{23} = 0.338E_2, \quad \nu_{12} = 0.32, \quad \nu_{23} = 0.49, \quad \alpha_1 / \alpha_0 = 0.001, \quad \alpha_2 / \alpha_0 = 1.0, \quad \rho =$$



Core (thickness  $h_c$ )

$$E_1 = 3.2 \times 10^{-5}, E_2 = 2.9 \times 10^{-5}, E_3 = 0.4, G_{12} = 2.4 \times 10^{-3}, G_{13} = 0.7.9 \times 10^{-2}, G_{23} = 6.6 \times 10^{-2},$$

$$\nu_{12} = 0.99, \nu_{23} = \nu_{32} = 3.0 \times 10^{-5}, \alpha_1 = \alpha_2 = 1.36\alpha_0, \rho_c = 0.07\rho$$

**Table 4**

Normalized natural frequency and critical temperature of 1 layer cross-ply ( $0^\circ$ ) and 3 layer cross-ply ( $0^\circ/90^\circ/0^\circ$ ) laminated composite square plates

| $a/h$ | $0^\circ$               |                         | $0^\circ/90^\circ/0^\circ$ |                         |
|-------|-------------------------|-------------------------|----------------------------|-------------------------|
|       | $\Omega$                | $\lambda_{cr}$          | $\Omega$                   | $\lambda_{cr}$          |
| 100   | $0.1231 \times 10^{-2}$ | $0.7491 \times 10^{-3}$ | $0.1231 \times 10^{-2}$    | $0.9946 \times 10^{-3}$ |
| 50    | $0.4898 \times 10^{-2}$ | $0.2960 \times 10^{-2}$ | $0.4893 \times 10^{-2}$    | $0.3927 \times 10^{-2}$ |
| 20    | $0.2968 \times 10^{-1}$ | $0.1736 \times 10^{-1}$ | $0.2951 \times 10^{-1}$    | $0.2290 \times 10^{-1}$ |
| 10    | 0.1079                  | $0.5746 \times 10^{-1}$ | 0.1061                     | $0.7417 \times 10^{-1}$ |
| 5     | 0.3354                  | 0.1414                  | 0.3254                     | 0.1743                  |

**Table 5**

Normalized natural frequency and critical temperature of 21 layer cross-ply  $[0^\circ/90^\circ/ \dots/90^\circ]_{10}$ [Core] $[90^\circ/90^\circ/ \dots/0^\circ]_{10}$  sandwich square plate with simply supported boundary conditions at different thickness ratio

| $h_f/h$ | $a/h$                   |                         |                         |                         |                         |                         |                         |                |
|---------|-------------------------|-------------------------|-------------------------|-------------------------|-------------------------|-------------------------|-------------------------|----------------|
|         | 100                     |                         | 50                      |                         | 20                      |                         | 10                      |                |
|         | $\Omega$                | $\lambda_{cr}$          | $\Omega$                | $\lambda_{cr}$          | $\Omega$                | $\lambda_{cr}$          | $\Omega$                | $\lambda_{cr}$ |
| 0.05    | $0.5207 \times 10^{-3}$ | $0.3995 \times 10^{-2}$ | $0.2053 \times 10^{-2}$ | $0.1551 \times 10^{-1}$ | $0.1257 \times 10^{-1}$ | $0.9260 \times 10^{-1}$ | $0.4717 \times 10^{-1}$ | 0.3211         |
| 0.1     | $0.7148 \times 10^{-3}$ | $0.3804 \times 10^{-2}$ | $0.2817 \times 10^{-2}$ | $0.1447 \times 10^{-1}$ | $0.1697 \times 10^{-1}$ | $0.8540 \times 10^{-1}$ | $0.6083 \times 10^{-1}$ | 0.2715         |
| 0.15    | $0.8482 \times 10^{-3}$ | $0.3583 \times 10^{-2}$ | $0.8377 \times 10^{-2}$ | $0.1398 \times 10^{-1}$ | $0.1991 \times 10^{-1}$ | $0.7866 \times 10^{-1}$ | $0.6889 \times 10^{-1}$ | 0.2338         |
| 0.2     | $0.9515 \times 10^{-3}$ | $0.3388 \times 10^{-2}$ | $0.3756 \times 10^{-2}$ | $0.1319 \times 10^{-1}$ | $0.2206 \times 10^{-1}$ | $0.7266 \times 10^{-1}$ | $0.7433 \times 10^{-1}$ | 0.2050         |
| 0.3     | $0.1101 \times 10^{-2}$ | $0.9870 \times 10^{-2}$ | $0.4339 \times 10^{-2}$ | $0.1176 \times 10^{-1}$ | $0.2506 \times 10^{-1}$ | $0.6264 \times 10^{-1}$ | $0.8143 \times 10^{-1}$ | 0.1648         |

The Normalized natural frequencies and critical temperatures obtained for different thickness ratio by varying the face thickness ( $h_f$ ) to total thickness ( $h$ ) ratio and using the present finite element are shown in Table 5. All these results are new.

### 3.5 Effect of aspect ratio, thickness ratio on cross-ply $[90^\circ/-90^\circ/ \dots/-90^\circ]$

In this example, a 10 layer plate has been analyzed with the same temperature loadings mentioned above. The material properties (dimensionless) of individual layers are as given below:

$$E_1 / E_2 = 15, G_{12} = G_{13} = 0.5E_2, G_{23} = 0.3356E_2, \nu_{12} = 0.3, \nu_{23} = 0.49, \alpha_1 / \alpha_0 = 0.015, \alpha_2 / \alpha_0 = 1.0, \rho = 1$$

The Normalized natural frequencies and critical temperatures obtained with different aspect ratio ( $a/b$ ) using the present finite element approach are shown in Table 6. All these results are presented for the first time.

### 3.6 Clamped cross-ply ( $0^\circ/90^\circ/0^\circ/90^\circ$ ) anti-symmetric laminate

The present problem of composite square plate ( $0^\circ/90^\circ/0^\circ/90^\circ$ ) has been solved with the uniform temperature rise throughout the thickness. The material properties (dimensionless) of individual layers are as given below:


$$E_1 / E_2 = 15, G_{12} = G_{13} = 0.5E_2, G_{23} = 0.3356E_2, \nu_{12} = 0.3, \nu_{23} = 0.49, \alpha_1 / \alpha_0 = 0.015, \alpha_2 / \alpha_0 = 1.0, \rho = 1$$

*Example 1:* In this section, anti-symmetric cross-ply ( $0^0/90^0/0^0/90^0$ ) with clamped boundary conditions subjected to uniform temperature rise throughout the thickness has been considered. The normalized natural frequencies with different thickness ratio ( $a/h$ ) are plotted in Fig. 2.

**Table 6**


Normalized natural frequency and critical temperature of 10 layer cross-ply [ $90^0/-90^0/.../-90^0$ ] laminated composite square plate with simply supported boundary conditions with different aspect ratio ( $a/b$ )

| $a/h$ | $a/b$ | $\Omega$                | $\lambda_{cr}$          |
|-------|-------|-------------------------|-------------------------|
| 100   | 1     | $0.1232 \times 10^{-2}$ | $0.7496 \times 10^{-3}$ |
|       | 1.5   | $0.2591 \times 10^{-2}$ | $0.1690 \times 10^{-2}$ |
|       | 2     | $0.4503 \times 10^{-2}$ | $0.3026 \times 10^{-2}$ |
| 50    | 1     | $0.4899 \times 10^{-2}$ | $0.2960 \times 10^{-2}$ |
|       | 1.5   | $0.1025 \times 10^{-1}$ | $0.6580 \times 10^{-2}$ |
|       | 2     | $0.1769 \times 10^{-1}$ | $0.1153 \times 10^{-1}$ |
| 20    | 1     | $0.2268 \times 10^{-1}$ | $0.1736 \times 10^{-1}$ |
|       | 1.5   | $0.6002 \times 10^{-1}$ | $0.3592 \times 10^{-1}$ |
|       | 2     | $0.9915 \times 10^{-1}$ | $0.5764 \times 10^{-1}$ |
| 10    | 1     | 0.1079                  | $0.5745 \times 10^{-1}$ |
|       | 1.5   | 0.2006                  | 0.1018                  |
|       | 2     | 0.3059                  | 0.1416                  |
| 5     | 1     | 0.3354                  | 0.1413                  |
|       | 1.5   | 0.5488                  | 0.2019                  |
|       | 2     | 0.7720                  | 0.2440                  |

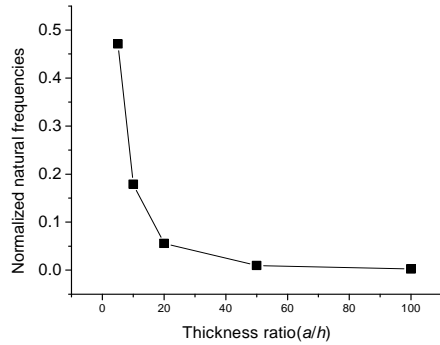

**Fig. 2**

Variation of natural frequencies of laminated composite clamped plates ( $0^0/90^0/0^0/90^0$ ) with different thickness ratio ( $a/h$ ).

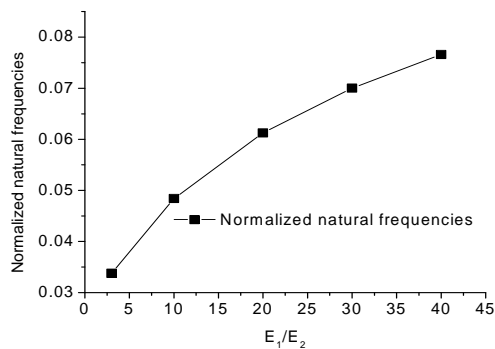

**Fig. 3**

Variation of natural frequencies of laminated composite clamped plates ( $0^0/90^0/0^0/90^0$ ) with different modular ratio ( $E_1/E_2$ ).

*Example 2:* In this example anti-symmetric cross-ply ( $0^0/90^0/0^0/90^0$ ) with clamped boundary conditions subjected to uniform temperature rise throughout the thickness has been considered. The Normalized natural frequencies with different modular ratio ( $E_1/E_2$ ) with thickness ratio ( $a/h = 20$ ) are plotted in Fig. 3.

### 3.7 Cross-ply sandwich square plate with simply supported at all the edges

In this section, five layer cross-ply sandwich plate ( $0^0/90^0/\text{Core}/90^0/0^0$ ) with different boundary conditions for  $h/h = 0.3$  subjected to uniform temperature rise throughout the thickness has been investigated. Results of normalized frequencies and critical temperatures are presented in Table 7. All the results are new.

**Table 7**

Normalized Natural frequency ( $\Omega$ ) and critical temperature ( $\lambda_{cr}$ ) of a simply supported laminated square sandwich plate ( $0^0/90^0/\text{Core}/90^0/0^0$ ) for different thickness ratio ( $a/h$ )

| Boundary Condition | Parameter      | $a/h$                   |                         |                         |                         |        |
|--------------------|----------------|-------------------------|-------------------------|-------------------------|-------------------------|--------|
|                    |                | 100                     | 50                      | 20                      | 10                      | 5      |
| SSSS               | $\Omega$       | $0.1099 \times 10^{-2}$ | $0.4340 \times 10^{-2}$ | $0.2502 \times 10^{-1}$ | $0.8102 \times 10^{-1}$ | 0.2114 |
|                    | $\lambda_{cr}$ | $0.3026 \times 10^{-2}$ | $0.1177 \times 10^{-1}$ | $0.6243 \times 10^{-1}$ | 0.1631                  | 0.2777 |
| SSSC               | $\Omega$       | $0.1367 \times 10^{-2}$ | $0.5346 \times 10^{-2}$ | $0.2938 \times 10^{-1}$ | $0.8867 \times 10^{-1}$ | 0.2205 |
|                    | $\lambda_{cr}$ | $0.4288 \times 10^{-2}$ | $0.1644 \times 10^{-1}$ | $0.8080 \times 10^{-1}$ | 0.1874                  | 0.2910 |
| SSCC               | $\Omega$       | $0.1748 \times 10^{-2}$ | $0.6732 \times 10^{-2}$ | $0.3462 \times 10^{-1}$ | $0.9733 \times 10^{-1}$ | 0.2328 |
|                    | $\lambda_{cr}$ | $0.6740 \times 10^{-2}$ | $0.2515 \times 10^{-1}$ | 0.1090                  | 0.2194                  | 0.3124 |
| SSSF               | $\Omega$       | $0.8064 \times 10^{-3}$ | $0.3182 \times 10^{-2}$ | $0.3108 \times 10^{-1}$ | $0.5978 \times 10^{-1}$ | 0.1571 |
|                    | $\lambda_{cr}$ | $0.3285 \times 10^{-2}$ | $0.1277 \times 10^{-1}$ | $0.6795 \times 10^{-1}$ | 0.1791                  | 0.3086 |
| SSFF               | $\Omega$       | $0.7856 \times 10^{-3}$ | $0.3099 \times 10^{-2}$ | $0.1792 \times 10^{-1}$ | $0.5833 \times 10^{-1}$ | 0.1527 |
|                    | $\lambda_{cr}$ | $0.3178 \times 10^{-2}$ | $0.1236 \times 10^{-1}$ | $0.6606 \times 10^{-1}$ | 0.1748                  | 0.2999 |

## 4 CONCLUSIONS

Natural frequencies of laminated composite and sandwich plates subjected to thermal loading have been analyzed by using the higher order zigzag theory for the first time in this paper. Since very few results are available in the literature based on a refined theory like the present one, the accuracy of natural frequencies and critical temperatures of laminated composite and sandwich plates subjected to thermal stresses has been studied by using present zigzag theory in detail. It has been established through various numerical examples that the present higher order zigzag theory can accurately predict the natural frequencies of general laminated composite and sandwich plates under thermal loading. As such the present model may be recommended for generating further results in the field.

## REFERENCES

- [1] Noor A.K., Burton W.S., 1992, Three-dimensional solutions for the free vibrations and buckling of thermally stressed multilayered angle-ply composite plates, *ASME Journal of Applied Mechanics* **59**(12): 868-877.
- [2] Matsunaga H., 2007, Free vibration and stability of angle-ply laminated composite and sandwich plates under thermal loading, *Composite Structures* **77**: 249-262.
- [3] Reddy J.N., Phan N.D., 1985, Stability and vibration of isotropic, orthotropic and laminated plates according to a higher-order shear deformation theory, *Journal of Sound and Vibration* **98**: 157-170.
- [4] Pucha N.S., Reddy J.N., 1986, Stability and natural vibration analysis of laminated plates by using a mixed element based on a refined plate theory, *Journal of Sound and Vibration* **104** (2): 285-300.
- [5] Tessler A., Saether E., Tsui T., 1995, Vibration of thick laminated composite plates, *Journal of Sound and Vibration* **179**: 475-498.
- [6] Ganapathi M., Makhecha D.P., 2001, Free vibration analysis of multi-layered composite laminates based on an accurate higher-order theory, *Composites: Part B* **32**: 535-543.
- [7] Shi J.W., Nakatani A., Kitagawa H., 2004, Vibration analysis of fully clamped arbitrarily laminated plate, *Composite Structures* **63**:115-122.

- [8] Khare R.K., Kant T., Garg A.K., 2004, Free vibration of composite and sandwich laminates with a higher-order facet shell element, *Composite Structures* **65**: 405-418.
- [9] Carrera E., 1998, Layer-wise mixed models for accurate vibrations analysis of multilayered plates, *ASME Journal of Applied Mechanics* **65**: 820-828.
- [10] Nosier A., Kapania R.K., Reddy J.N., 1993, Free vibration analysis of laminated plates using a layer wise theory, *Journal of American Institute of Aeronautics and Astronautics* **31**(12):2335-2346.
- [11] Cho K.N., Bert C.W., Striz A.G., 1991, Free vibrations of laminated rectangular plates analyzed by higher order individual-layer theory, *Journal of Sound and Vibration* **145**(3): 429-442.
- [12] Khdeir A.A., Reddy J.N., 1999, Free vibration of laminated composite plates using second-order shear deformation theory, *Computers and Structures* **71**: 617-626.
- [13] Messina A., 2001, Two generalized higher order theories in free vibration studies of multilayered plates, *Journal of Sound and Vibration* **242**(1): 125-150.
- [14] Shu X., 2001, Vibration and bending of anti symmetrically angle-ply laminated plates with perfectly and weakly bonded layers, *Composite Structures* **53**: 245-255.
- [15] Singh B.N., Yadav D., Iyengar N.G.R., 2001, Natural frequencies of composite plates with random material properties using higher order shear deformation theory, *International Journal of Mechanical Science* **43**: 2193-2214.
- [16] Kapuria S., Achary G.G.S., 2004, An efficient higher-order zigzag theory for laminated plates subjected to thermal loading, *International Journal of Solids and Structures* **41**: 4661-4684.
- [17] Matsunaga H., 2004, A comparison between 2-D single-layer and 3-D layer wise theories for computing inter laminar stresses of laminated composite and sandwich plates subjected to thermal loadings, *Composite Structures* **64**(2): 161-177.
- [18] Wang X., Dong K., Wang X.Y., 2005, Hygro thermal effect on dynamic inter laminar stresses in laminated plates with piezoelectric actuators, *Composite Structures* **71**: 220-228.
- [19] Zhen W., Wanji C., 2006, An efficient higher-order theory and finite element for laminated plates subjected to thermal loading, *Composite Structures* **73**: 99-109.
- [20] Matsunaga H., 2005, Thermal buckling of cross-ply laminated composite and sandwich plates according to a global higher-order deformation theory, *Composite Structures* **68**(4): 439-454.
- [21] Matsunaga H., 2006, Thermal buckling of angle-ply laminated composite and sandwich plates according to a global higher-order deformation theory, *Composite Structures* **72**(2): 177-192.
- [22] Matsunaga H., 2007, Free vibration and stability of angle-ply laminated composite and sandwich plates under thermal loading. *Composite Structures* **77**: 249-262.
- [23] Naganarayana B.P., Rama Mohan P., Prathap G., 1997, Accurate thermal stress predictions using  $C^0$  continuous higher-order shear deformable elements. *Computer Methods in Applied Mechanics and Engineering* **144**: 61-75.